



**Figure 7:** Attractive patterns are shown by these colour-zoned Iranian demantoid/andradite slices, which weigh 1.68 ct (left) and 1.08 ct (right). The faceted stones at the bottom centre were cut so that darker green colour zones are centred under their tables; they weigh 0.67 ct (left) and 0.52 ct (right). Photo by Bradley J. Payne.

## Blue Diopside from Russia

*Violane* (or *violan*) is a term used for violet to blue diopside with a massive polycrystalline texture that mainly has been mined from the Praborna manganese deposit in St Marcel, Italy, and is coloured by Mn (Mottana *et al.* 1979). Although known for decades, this ornamental material is rarely mentioned in the gemmological literature (cf. Webster 1949). The term *violane* has also been applied to massive polycrystalline blue diopside from Russia, particularly by sellers on the Internet. In addition, similar material is known from Baffin Island, Canada, which is coloured by  $\text{Fe}^{2+}$ - $\text{Ti}^{4+}$  intervalence charge transfer (Herd *et al.* 2000).

During the February 2020 Tucson gem shows, Rare Earth Mining Co. (Trumbull, Connecticut, USA) displayed some blue and blue/white cabochons represented as *violane*. According to Rare Earth's Bill Heher, the rough material came to market in around August 2018 and was mined from the Lake Baikal region of Russia. So far he has cut a few hundred cabochons that ranged up to about 50 mm in maximum dimension.

Ornamental blue diopside is known from three localities in Russia: the Khakassia area of eastern Siberia (Shil'tsina & Vereshchagin 2000) and two areas near Lake Baikal (Zadov *et al.* 2004; Simakin *et al.* 2019). According to D. Belakovskiy (pers. comm. 2020), the Lake Baikal deposits are hosted by (1) the Yoko-Dovyrenskiy (or Yoko-Dovyren) massif near the north end of the lake and (2) the Tazheranskiy (or Tazheran) massif near the lake's south end.

Heher loaned three samples for examination (Figure 8), and they were characterised by authors CW and

outer surfaces along their edges. The slices that Payne obtained ranged from 1 to 2 ct and the faceted stones weighed 0.15–1.25 ct.

Although demantoid/andradite from Iran has been known since 2001, this is the first time that this author is aware of this material being cut into polished slices to showcase its attractive colour zoning—as is commonly done with multicoloured tourmaline.

Brendan M. Laurs FGA


## Reference

- Karampelas, S., Gaillou, E., Fritsch, E. & Douman, M. 2007. Gem News International: Color-zoned andradite from Iran, with calcite inclusions. *Gems & Gemology*, **43**(1), 65–67.

BW. They consisted of a blue oval cabochon weighing 17.88 ct (27.50 × 21.27 mm), and a matched pair of bicoloured blue and white/tan rectangular cabochons with a total weight of 35.71 ct (each measuring approximately 26 × 15 mm). All displayed an obvious polycrystalline structure that was fine- to coarse-grained and showed variable depth of blue colour between grains in the blue portions (Figure 9). A few sparkles seen as the samples were moved apparently corresponded to cleavage fractures in some of the diopside grains. Viewed with the microscope, the blue areas of the samples also exhibited variations in surface lustre between grains (again, see Figure 9). Although individual grains were somewhat transparent, the presence of abundant polycrystalline



**Figure 8:** These three cabochons containing blue diopside (17.57–17.88 ct) are from Russia's Lake Baikal region and were studied for this report. Photo by B. Williams.

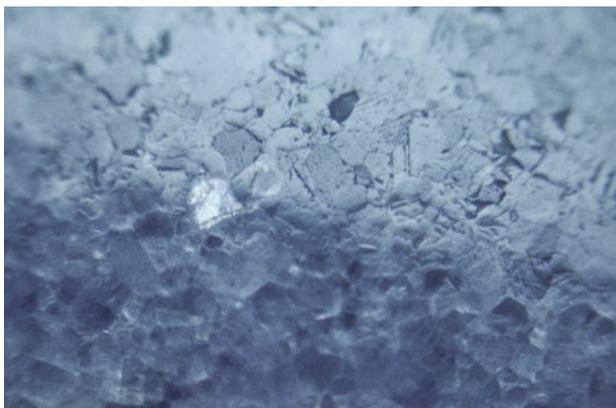


**Figure 9:** Microscopic examination of the blue diopside shows a polycrystalline texture with variations in surface lustre between grains and a reflection from a cleavage fracture (left centre). Photomicrograph by B. Williams and C. Williams, in reflected light; image width 9 mm.

grain boundaries created an overall semi-translucent appearance in the blue areas.

All three samples were confirmed as diopside in the blue areas by Raman analysis using a Magilabs Gemmo-Raman-532SG spectrometer. A Raman peak shift was observed in the white/tan area of the bicoloured stones, which might be due to the presence of additional mineral phases occurring with the diopside. Indeed, Simakin *et al.* (2019) reported that ‘bleached’ metasomatised zones associated with blue diopside from Lake Baikal consist of recrystallised white diopside and monticellite, while Zadov *et al.* (2004) indicated that the light-coloured zones consisted of foshagite and other minerals.

Spot RI readings of the cabochons could not be obtained due to the polycrystalline nature of the material. The hydrostatic SG value of the blue sample was 3.23, which is slightly lower than the typical range for diopside (3.24–3.33) but consistent with its polycrystalline structure. The stones were inert to long- and short-wave UV radiation. Energy-dispersive X-ray fluorescence (EDXRF) chemical analysis of the blue sample performed with an Amptek X123-SDD spectrometer showed traces of the chromophoric elements V, Fe and Cr (as well as very small amounts of Pt, consistent with blue diopside from the Yoko-Dovyren massif documented by Simakin *et al.* 2019).

Simakin *et al.* (2019) reported an average of 345 ppm V in blue diopside from the Lake Baikal area, and attributed its colouration to  $\text{VO}^{2+}$ . Visible-near infrared (Vis-NIR) absorption spectroscopy of the present blue cabochon with a Magilabs GemmoSphere spectrometer showed a large broad peak centred at about 630 nm and a smaller absorption at about 430 nm (Figure 10). This pattern is indeed consistent with colouration due

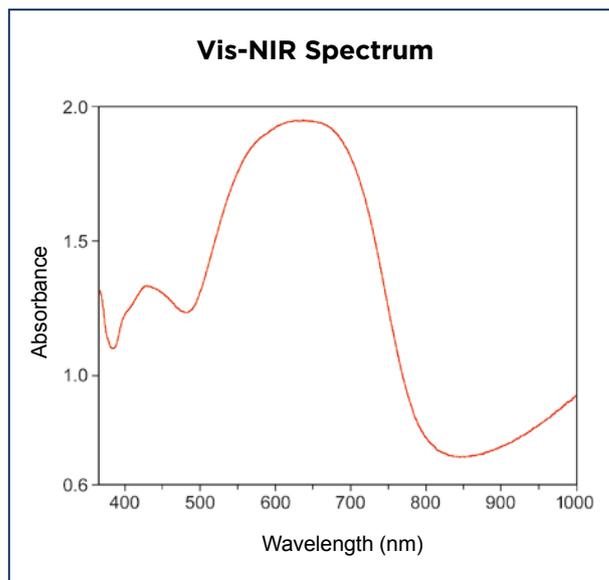

**Figure 10:** Vis-NIR spectroscopy of the blue diopside shows a large broad peak centred at about 630 nm and a smaller absorption at about 430 nm, consistent with colouration due to  $\text{VO}^{2+}$ .

to tetravalent vanadium in the form of the vanadyl ion ( $\text{VO}^{2+}$ ), as seen for example in cavansite (Rossman 2014). Vanadium-doped synthetic diopside also shows distinct blue colouration and a similar absorption spectrum (see, e.g., sample GRR 510 at <https://minerals.gps.caltech.edu/FILES/Visible/pyroxene/Index.html>). Taken together, all of these aspects provide confirmation that the blue colouration of the Russian diopside studied for this report is due to  $\text{VO}^{2+}$ .

*Acknowledgement:* We thank Dmitriy Belakovsky (curator of the Fersman Mineralogical Museum, Moscow) for providing information and references on blue diopside from Russia.

Cara Williams FGA and Bear Williams FGA  
([info@stonegrouplabs.com](mailto:info@stonegrouplabs.com))  
Stone Group Laboratories  
Jefferson City, Missouri, USA

Brendan M. Laurs FGA

## References

- Herd, C.D.K., Peterson, R.C. & Rossman, G.R. 2000. Violet-colored diopside from southern Baffin Island, Nunavut, Canada. *Canadian Mineralogist*, **38**(5), 1193–1199, <https://doi.org/10.2113/gscanmin.38.5.1193>.
- Mottana, A., Rossi, G., Kracher, A. & Kurat, G. 1979. Violan revisited: Mn-bearing omphacite and diopside. *Tschermaks Mineralogische und Petrographische Mitteilungen*, **26**(3), 187–201, <https://doi.org/10.1007/bf01081845>.

Rossmann, G.R. 2014. Optical spectroscopy. *Spectroscopic Methods in Mineralogy and Materials Sciences*, Reviews in Mineralogy and Geochemistry, Vol. 78, Mineralogical Society of America, Chantilly, Virginia, USA, 371–398, <https://doi.org/10.2138/rmg.2014.78.9>.

Shil'tsina, A.D. & Vereshchagin, V.I. 2000. Ceramic tiles containing diopside and clay raw materials from Khakassia. *Glass and Ceramics*, 57(3–4), 87–90, <https://doi.org/10.1007/bf02681515>.

Simakin, A.G., Kislov, E.V., Salova, T.P., Shaposhnikova, O.Y. & Nekrasov, A.N. 2019. Reduced CO<sub>2</sub> fluid as

an agent of ore-forming processes: A case study of dolomite-replacement skarns at the Yoko-Dovyren massif. *Petrology*, 27(1), 1–16, <https://doi.org/10.1134/S086959111901003x>.

Webster, R. 1949. The identification of gemstones by colour. *The Gemmologist*, 18(215), 152–155.

Zadov, A.E., Pertsev, N.N., Belakovskiy, D.I., Chukanov, N.V. & Kuznetsova, O.Yu. 2004. Foshagite and hillebrandite from skarn xenoliths of Ioko-Dovyrensky massif. *Proceedings of the Russian Mineralogical Society*, 133(1), 73–83 (in Russian with English abstract).

## A Collection of Cat's-Eye Emeralds from Colombia

Fine cat's-eye emeralds are quite rare, and have been documented mostly from Brazil (e.g. Laurs 2012 and references therein). However, flattened cabochons showing chatoyancy have been reported from Colombia—specifically the Coscuez mine in the Muzo region (Johnson & Koivula 1996). More recently, Weldon and McClure (2013) described the cutting of a fine matched pair of Colombian cat's-eye emeralds that weighed 75 ct by husband-and-wife gem cutters Misael Angel Rodríguez and Claudia Patricia Beltrán Rubiano.

During the February 2020 Tucson gem shows, the same emerald cutters showed this author an impressive collection of 24 cat's-eye emeralds from Colombia (Figure 11). The stones ranged from 0.49 to 3.81 ct and had a total weight of 37.90 carats. The collection was assembled during 2019 from polished stones that they obtained on the market in Colombia; all of them had undergone clarity enhancement with cedarwood oil. According to them, the stones showed characteristics consistent with being cut from trapiche rough material mined in the Muzo area.

The cat's-eye effect was best seen when the stones were displayed over a light-coloured reflective background. Moreover, the chatoyancy appeared to be caused by very fine-scale, parallel, transparent structures, which likely correspond to the dislocations that were documented by Pignatelli *et al.* (2015) in the 'arms' of Colombian trapiche emeralds. These bundles of straight dislocations are oriented perpendicular to  $\{10\bar{1}0\}$  faces, commonly with parallel elongated voids and trains of fluid inclusions. As documented by Weldon and McClure (2013),

rough material obtained from the arms of trapiche crystals can be polished into attractive cat's-eye cabochons if it contains the appropriate structural properties and is suitably oriented. As awareness grows of the potential for cutting cat's-eyes from trapiche rough material, these rare chatoyant emeralds from Colombia may become more available in the future.

Brendan M. Laurs FGA



**Figure 11:** Cat's-eye emeralds from Colombia are quite rare. The 24 stones in this impressive collection weigh 0.49–3.81 ct. Photo by Jeff Scovil.